

10-10-1973

# Stable Single-Domain to Superparamagnetic Transition During Low-Temperature Oxidation of Oceanic Basalts

Robert F. Butler  
*University of Portland*, [butler@up.edu](mailto:butler@up.edu)

Follow this and additional works at: [http://pilotscholars.up.edu/env\\_facpubs](http://pilotscholars.up.edu/env_facpubs)

 Part of the [Environmental Sciences Commons](#), [Geology Commons](#), and the [Geophysics and Seismology Commons](#)

---

## Citation: Pilot Scholars Version (Modified MLA Style)

Butler, Robert F., "Stable Single-Domain to Superparamagnetic Transition During Low-Temperature Oxidation of Oceanic Basalts" (1973). *Environmental Studies Faculty Publications and Presentations*. Paper 20.  
[http://pilotscholars.up.edu/env\\_facpubs/20](http://pilotscholars.up.edu/env_facpubs/20)

This Journal Article is brought to you for free and open access by the Environmental Studies at Pilot Scholars. It has been accepted for inclusion in Environmental Studies Faculty Publications and Presentations by an authorized administrator of Pilot Scholars. For more information, please contact [library@up.edu](mailto:library@up.edu).

## Stable Single-Domain to Superparamagnetic Transition during Low-Temperature Oxidation of Oceanic Basalts

ROBERT F. BUTLER

*Department of Geology and Geophysics, University of Minnesota  
Minneapolis, Minnesota 55455*

Recent experimental data on synthetic titanomaghemites indicate that oxidation is accompanied by a decrease in magnetocrystalline anisotropy  $K_1$  as well as a decrease in the saturation magnetization  $\sigma_s$ . Theory of relaxation times predicts that the decrease of  $\sigma_s$  and  $K_1$  with oxidation will cause single-domain titanomagnetite grains with initially low blocking temperatures to become superparamagnetic as they are oxidized to titanomaghemite. For titanomagnetites ( $\text{Fe}_{x-2}\text{Ti}_x\text{O}_4$ ) of composition  $x = 0.4$  and  $x = 0.5$  the affected blocking temperature range is approximately  $200^\circ$  and  $125^\circ\text{K}$  below the Curie point, respectively. However, for  $x = 0.6$  titanomagnetites the blocking temperature range affected is within  $80^\circ\text{K}$  of the Curie point and spans a temperature interval from  $325^\circ$  to as high as  $380^\circ\text{K}$ , depending on the degree of oxidation. The rapid quenching of oceanic pillow lavas (average composition  $x \cong 0.6$ ) produces efficient thermoremanence carriers but will also result in a significant grain size and blocking temperature distribution. Thus low-temperature oxidation of oceanic basalts could cause a significant portion of the originally stable carriers of natural remanence to become superparamagnetic. This mechanism could aid in explaining the large natural remanent magnetization intensity decrease of dredged basalts with distance from the mid-Atlantic ridge.

In a series of articles concerning dredged basalts from the mid-Atlantic ridge at  $45^\circ\text{N}$  by *Irving et al.* [1970], *Schaeffer and Schwarz* [1970], *Carmichael* [1970], *Park and Irving* [1970], and *Irving* [1970] a 90% decrease in natural remanent magnetization (NRM) intensity was found as the sample localities moved from the median valley to the ridge flanks. *Irving et al.* [1970] found that most of this large decrease occurred over a distance of only 6 km from the median valley. At a half-spreading rate of 2 cm/yr this would represent only 0.3 m.y. Total iron content ( $\text{FeO} + \text{Fe}_2\text{O}_3$ ) was found to be constant, but the ferrous/ferric ratio ( $\text{FeO}/\text{Fe}_2\text{O}_3$ ) decreases sharply with distance from the ridge. Blocking temperature  $T_b$  and median destructive field (af field at which 50% of the NRM has been destroyed) were found to increase with distance from the ridge.

Curie point ( $T_c$ ), cell edge, and microprobe studies by *Schaeffer and Schwarz* [1970] indicate that the titanomagnetite phase of the dredged basalts has an Fe/Ti ratio of approximately 4.6. This ratio corresponds to a titanomag-

netite composition ( $\text{Fe}_{x-2}\text{Ti}_x\text{O}_4$ ) of  $x = 0.55$ . Curie point and cell edge data of *Carmichael* [1970] indicate an average composition of  $x \cong 0.6$ . Scanning electron microscopy has revealed the existence of abundant very-fine-particle ( $<1 \mu$ ) titanomagnetites in the dredged basalts [*Evans and Wayman*, 1972]. Such fine-particle titanomagnetites would be expected to act as single-domain or pseudo-single-domain carriers of remanent magnetization.

*Park and Irving* [1970] discovered that the ratio of NRM of the median valley rocks to NRM of samples from the ridge flanks could be decreased by comparing intensities after af demagnetization. However, the ratio never dropped below 3:1. This finding would suggest that viscous demagnetization of low-coercivity particles cannot entirely account for the NRM decrease with age. *Park and Irving* suggested that the variation in magnetic properties might be due to some type of oxidation process. *Carmichael* [1970] has attributed some of the NRM decrease to paleofield variations.

In a review and discussion of the series of articles on the mid-Atlantic ridge at  $45^\circ\text{N}$  *Irving* [1970] pointed out that the rapid quenching of basalt in the axial zone along

with the sulfide content of the basalts would produce very-fine-grained titanomagnetite grains with little or no high-temperature deuteric oxidation. These fine-grained titanomagnetites would be very efficient thermoremanent magnetization (TRM) carriers but would also be susceptible to low-temperature oxidation. The constant  $\text{FeO} + \text{Fe}_2\text{O}_3$  and decreasing  $\text{FeO}/\text{Fe}_2\text{O}_3$  ratio along with increasing  $\text{H}_2\text{O}$  content with distance from the median valley led Irving to suggest that the changes in magnetic properties of the dredged basalts could be due to oxidation of the original titanomagnetite to a cation-deficient titanomaghemite. The NRM decrease would then be caused partly by viscous demagnetization of low-coercivity grains and partly by oxidation of titanomagnetite to titanomaghemite.

On theoretical grounds *Marshall and Cox* [1972] excluded viscous demagnetization as a cause for the NRM intensity decrease. In a single pillow basalt fragment with varying degrees of oxidation, a 40% decrease in NRM intensity and saturation magnetization was found in the weathered zone, compared with the fresh interior. An increase in Curie point and median destructive field along with a decrease in cell edge was found with increasing degree of oxidation. *Marshall and Cox* thus proposed that the changes in magnetic properties with distance from the median valley found in the study reviewed by *Irving* [1970] are analogous to the changes observed with increasing degree of weathering within their single pillow basalt fragment. They further suggest that the NRM decrease with distance from the ridge is entirely due to maghemitization.

By spectral analysis of marine magnetic anomalies *Cox et al.* [1972] have shown that the source of the linear magnetic anomalies can best be modeled with a two-layer oceanic crust. The thin upper layer becomes less magnetic as it moves away from the ridge, whereas the thicker, initially less magnetic lower layer keeps its initial intensity of magnetization. Maghemitization of the upper layer is proposed as a mechanism for the decrease in intensity of magnetization.

*Banerjee* [1971, 1972] has suggested that an intrinsic decay mechanism due to ionic diffusion of  $\text{Fe}^{2+}$  ions in quenched titanomagnetites may lead to a decrease in remanence coercivity

with increasing age. This decrease could produce a decrease in NRM intensity that would add to the decrease due to oxidation.

*Readman and O'Reilly* [1972] have studied the magnetic properties of synthesized titanomaghemites with increasing degree of oxidation. Degree of oxidation  $z$  is defined as the fraction of total  $\text{Fe}^{2+}$  ions initially in the sample that have been converted to  $\text{Fe}^{3+}$ . *Readman and O'Reilly* oxidized very-fine-grained titanomagnetites ( $\text{Fe}_{3-x}\text{Ti}_x\text{O}_4$ ) with  $x = 0.0, 0.4, 0.7$ , and 1.0 to cation-deficient titanomaghemites by heating in air to 200°–300°C. Magnetic properties and weight changes of the samples were carefully monitored as oxidation proceeded. Curie temperature was found to increase with increasing  $z$ , whereas cell edge and saturation magnetization  $\sigma$ , decreased. Rotational hysteresis experiments on the  $x = 0.4$  sample suggest a strong decrease in the magnetocrystalline anisotropy constant  $K_1$  with increasing oxidation. Similar rotational hysteresis data on  $x = 0.5$  and  $x = 0.6$  also indicate a decrease in magnetocrystalline anisotropy with increasing  $z$  [*Manson*, 1972].

*Marshall and Cox* [1972] have pointed out that the decrease in  $\sigma$ , accompanying oxidation will decrease NRM intensity by diminishing the saturation magnetization of the stable single-domain grains in sea floor basalts. We propose that the decrease in  $\sigma$ , and  $K_1$  observed by *Readman and O'Reilly* will lead to an additional decrease in NRM intensity by causing a significant portion of titanomagnetite grains that, when they are unoxidized, are stable single-domain grains to become superparamagnetic as they are oxidized to titanomaghemite. Thus not only will the intensity of NRM due to the stable single-domain grains decrease by oxidation, but the number of such grains will be diminished by oxidation.

#### THEORY OF RELAXATION TIMES

According to *Neel* [1955] the relaxation time of a single-domain grain is given by

$$1/\tau_0 = C \exp(-vH_c\sigma_s/2kT) \quad (1)$$

where  $\tau_0$  is relaxation time in seconds,  $C$  is frequency factor of  $10^9 \text{ sec}^{-1}$ ,  $v$  is grain volume in cubic centimeters,  $H_c$  is coercive force of the grain in oersteds,  $\sigma_s$  is saturation magnetization in electromagnetic units per cubic centimeter,  $k$

is the Boltzmann constant, and  $T$  is absolute temperature. For cubic grains whose coercive force is determined by magnetocrystalline anisotropy [Chikazumi, 1964]

$$H_c = \frac{4}{3} K_1 / \sigma_s \quad (2)$$

where  $K_1$  is the magnetocrystalline anisotropy constant. If magnetocrystalline anisotropy is dominant, (1) will become

$$1/\tau_0 = C \exp(-2vK_1/3kT) \quad (3)$$

However, if shape anisotropy is dominant,

$$H_c = \Delta N_D \sigma_s \quad (4)$$

where  $\Delta N_D$  is the difference in self-demagnetizing factor between the polar and equatorial axes of ellipsoidal particles. For shape anisotropy, (1) will become

$$1/\tau_0 = C \exp(-v\Delta N_D \sigma_s^2 / 2kT) \quad (5)$$

Although  $\sigma_s$  decreases with increasing  $x$  and the absolute value of coercivity arising from shape anisotropy (for a given  $\Delta N_D$ ) decreases with increasing Ti content, the relative importance of shape anisotropy and magnetocrystalline anisotropy is not easy to predict. Syono [1965] reports that the room temperature magnetocrystalline anisotropy constant  $K_1$  also decreases with increasing  $x$  in the composition range of the dredged oceanic basalts ( $0.4 \leq x \leq 0.6$ ). In fact,  $K_1$  changes from negative to positive at  $x \hat{=} 0.65$ . Thus calculations of coercivities for titanomagnetites in the range  $0.4 \leq x \leq 0.6$  should consider both shape anisotropy and magnetocrystalline anisotropy. The possibility that coercive force could be controlled by magnetostriction will be discussed later.

At the blocking temperature  $T_B$  the relaxation time  $[\tau_0(T_B)]$  is given by

$$1/\tau_0(T_B) = C \exp[-2vK_1(T_B)/3kT_B] \quad (6)$$

for magnetocrystalline-controlled coercive force, where  $K_1(T_B)$  is the magnetocrystalline anisotropy constant at  $T_B$ . For shape-controlled coercivity the blocking temperature relaxation time will be

$$1/\tau_0(T_B) = C \exp\{-v\Delta N_D [\sigma_s(T_B)]^2 / 2kT_B\} \quad (7)$$

If the blocking temperature is known from thermal demagnetization experiments and a value can be assigned to  $\tau_0(T_B)$  by setting it approximately equal to the time spent at the blocking temperature during the experiment (e.g.,  $10^3$  sec), the volume of the grains with a given  $T_B$  can be calculated (when single-domain behavior is assumed) by

$$v = [\ln C\tau_0(T_B)] [3kT_B/2K_1(T_B)] \quad (8)$$

for magnetocrystalline anisotropy and by

$$v = \{\ln C\tau_0(T_B)\} \{2kT_B/\Delta N_D [\sigma_s(T_B)]^2\} \quad (9)$$

for shape anisotropy.

Given the activation volume  $v$  corresponding to various blocking temperatures, the relaxation time at room temperature ( $290^\circ\text{K}$ ) as a function of oxidation state  $z$  can be calculated by

$$1/\tau_0(290^\circ\text{K}, z) = C \exp[-vH_c(290^\circ\text{K}, z) \cdot \sigma_s(290^\circ\text{K}, z) / 2k \cdot 290^\circ\text{K}] \quad (10)$$

where  $H_c(290^\circ\text{K}, z)$  is the coercive force at  $290^\circ\text{K}$  and oxidation state  $z$  and  $\sigma_s(290^\circ\text{K}, z)$  is the saturation magnetization at  $290^\circ\text{K}$  and  $z$ ;  $H_c(290^\circ\text{K}, z)$  is

$$H_c(290^\circ\text{K}, z) = \frac{4}{3} K_1(290^\circ\text{K}, z) / \sigma_s(290^\circ\text{K}, z) \quad (11)$$

or

$$H_c(290^\circ\text{K}, z) = \Delta N_D \sigma_s(290^\circ\text{K}, z)$$

for magnetocrystalline and shape anisotropy, respectively, where  $K_1(290^\circ\text{K}, z)$  is the magnetocrystalline anisotropy constant at  $290^\circ\text{K}$  and oxidation state  $z$ . Substituting  $v$  from (8) and (9) and  $H_c(290^\circ\text{K}, z)$  from (11) into (10) yields

$$1/\tau_0(290^\circ\text{K}, z) = C \exp\{-[\ln C\tau_0(T_B)] \cdot [T_B K_1(290^\circ\text{K}, z) / K_1(T_B) \cdot 290^\circ\text{K}]\} \quad (12)$$

for magnetocrystalline anisotropy and

$$1/\tau_0(290^\circ\text{K}, z) = C \exp\{-[\ln C\tau_0(T_B)] \cdot [T_B (\sigma_s(290^\circ\text{K}, z))^2 / (\sigma_s(T_B))^2 \cdot 290^\circ\text{K}]\} \quad (13)$$

for shape anisotropy. Thus we should be able to calculate room temperature relaxation times as a function of blocking temperature of the unoxidized titanomagnetite and oxidation state

of the titanomaghemite resulting from low-temperature oxidation.

If  $\tau_0(290^\circ\text{K}, z)$  falls below a value that is less than the time span of interest to paleomagnetism, the grain can be considered to have become thermally unstable or superparamagnetic. Therefore knowledge of composition and blocking temperature of titanomagnetite in fresh oceanic lavas along with knowledge of the dependence of coercive force on oxidation state should allow us to determine what blocking temperature range will become superparamagnetic as a result of low-temperature oxidation to titanomaghemite. If a significant proportion of the NRM is contained in grains that are stable single domains when they are stoichiometric but that become superparamagnetic when they are oxidized to cation-deficient spinels, this mechanism could help to explain the large observed decrease in NRM intensity with distance from the median valley.

RELAXATION TIME CALCULATIONS

Unfortunately, not all the data required for calculation of  $\tau_0(290^\circ\text{K}, z)$  are presently available or easy to measure. Specifically,  $K_1$ - $T$  and  $\sigma_s$ - $T$  data are required. Syono [1965] gives  $K_1$ - $T/T_c$  for  $x = 0.31$  in the temperature range  $0.1 \leq T/T_c \leq 0.5$  and  $K_1$ - $T/T_c$  for  $x = 0.56$  in the range  $0.5 \leq T/T_c \leq 0.7$ . To determine  $K_1$ - $T$  for  $x = 0.4, 0.5,$  and  $0.6$  titanomagnetites, several extrapolations of the available data are required. First, we must extrapolate Syono's  $K_1$ - $T/T_c$  data for  $x = 0.31$  and  $0.56$  to the Curie temperature in some 'reasonable' fashion.

Such an extrapolation along with the original data is shown in Figure 1a. Second, we must interpolate the temperature dependence of  $K_1$  for  $x = 0.4, 0.5,$  and  $0.6$  from the dependence of  $K_1$  on  $T/T_c$  for  $x = 0.31$  and  $0.56$ . This interpolation can be accomplished by making the reasonable assumption that the form of  $K_1$ - $T/T_c$  will be similar for  $x = 0.4$  and  $0.31$  and that similarity of form will exist between  $x = 0.5, 0.56,$  and  $0.6$ . Thus  $K_1$ - $T/T_c$  for  $x = 0.4$  can be estimated by

$$K_1(x = 0.4, T/T_c) = [K_1(0.4, 290^\circ\text{K}) \cdot K_1(0.31, T/T_c) / K_1(0.31, 290^\circ\text{K})]$$

where  $K_1(0.4, 290^\circ\text{K})$  and  $K_1(0.31, 290^\circ\text{K})$  are the room temperature magnetocrystalline anisotropy constants taken from Syono [1965]. The resulting  $K_1$ - $T$  curves for  $x = 0.4, 0.5,$  and  $0.6$  are shown in Figure 1b. Room temperature relaxation time calculations for titanomagnetite grains whose coercivity is controlled by magnetocrystalline anisotropy can now be made.

Similar relaxation time calculations for grains whose coercive force is dominated by shape anisotropy can be made only if we know the temperature dependence of  $\sigma_s$ . Stephenson [1972a] theoretically derived normalized  $\sigma_s$ - $T/T_c$  curves for  $0 \leq x \leq 0.95$ . The solid line plots of  $\sigma_s$ - $T$  in Figure 2 were calculated by using the normalized  $\sigma_s$ - $T/T_c$  calculations of Stephenson along with  $\sigma_s$ - $x$  data from O'Reilly and Banerjee [1965].

However, comparison of Stephenson's [1972b] predicted  $\sigma_s$ - $T/T_c$  behavior for pure magnetite

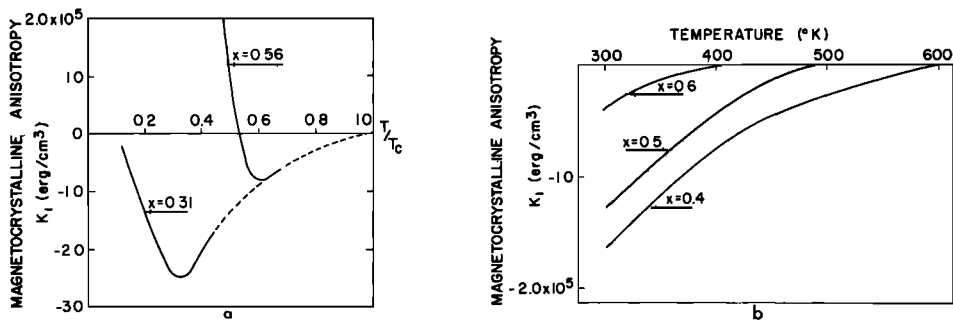


Fig. 1. Magnetocrystalline anisotropy constant  $K_1$  (a) as a function of  $T/T_c$  (the solid lines are from Syono [1965], whereas the dashed lines are extrapolations; the extrapolated curves overlap for  $T/T_c > 0.7$ ) and (b) as a function of temperature for titanomagnetites of composition  $x = 0.4, 0.5,$  and  $0.6$  (the curves were derived from assumed similarity of the form of  $K_1$ - $T/T_c$  for  $x = 0.31$  and  $x = 0.4$  and similarity of  $K_1$ - $T/T_c$  for  $0.5, 0.56,$  and  $0.6$ ).

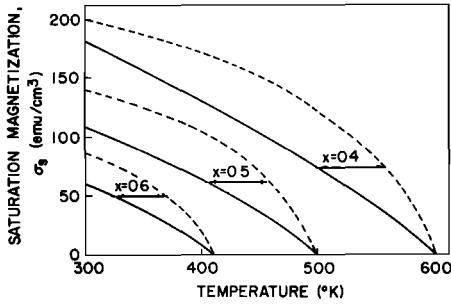


Fig. 2. Saturation magnetization  $\sigma_s$  versus temperature for titanomagnetite of  $x = 0.4, 0.5,$  and  $0.6$ . Normalized magnetization versus  $T/T_c$  plots of Stephenson [1972a] and  $\sigma_s-x$  data from O'Reilly and Banerjee [1965] were used to calculate the solid curves. The experimental  $\sigma_s-T/T_c$  curve of Weiss [1907] was used to derive the dashed curves.

does not agree with the experimental curve of Weiss [1907]. Stephenson suggests that the discrepancy is due to positive  $Fe^{3+}Fe^{2+}$  BB interactions that have been neglected in his theoretical treatment. Since B site  $Fe^{3+}$  concentration decreases with increasing  $x$ , theory and experiment should be in better agreement as  $x$  increases.

Because the accuracy of Stephenson's theoretical model for titanomagnetites is unconfirmed,  $\sigma_s-T$  curves for  $x = 0.4, 0.5,$  and  $0.6$  were also calculated by using the experimental  $\sigma_s-T/T_c$  data of Weiss [1907] for magnetite on the assumption that the normalized  $\sigma_s-T/T_c$  behavior will not change with increasing  $x$ . The

resulting plots are shown by dashed lines in Figure 2. The actual  $\sigma_s-T$  behavior will likely fall between these curves. Thus results obtained by using either the Stephenson [1972a] theoretical  $\sigma_s-T$  curve or the Weiss [1907] experimental curve should be considered extrema, the actual behavior falling between the two.

Room temperature relaxation times as a function of oxidation state can be calculated by (12) and (13) if the dependence of  $K_1$  and  $\sigma_s$  on oxidation state is known. These dependences can be estimated from the data of Readman and O'Reilly [1972] and Manson [1972].

Saturation magnetization ( $4.2^\circ K$ ) as a function of oxidation state is given in terms of Bohr magnetons  $\mu_B$  per molecule for  $x = 0.4$  and  $x = 0.7$  in Figure 2 of Readman and O'Reilly [1972]. If we assume that the form of  $\sigma_s-z$  for  $x = 0.5$  will follow that of  $\sigma_s-z$  for  $x = 0.4$  and that  $\sigma_s-z$  for  $x = 0.6$  will be similar in form to the data given for  $x = 0.7$ , the oxidation state dependences of saturation magnetization shown in Figure 3a can be derived. Since the saturation magnetization versus  $z$  data of Readman and O'Reilly [1972] were determined at  $4.2^\circ K$ , they must be adjusted to room temperature. As was true with the  $\sigma_s-T$  curves of Figure 2, both the Stephenson [1972a] and Weiss [1907]  $\sigma_s-T/T_c$  curves were used for this adjustment from  $4.2^\circ$  to  $290^\circ K$ . The increase in Curie temperature with increasing  $z$  has also been taken into account in deriving the room temperature  $\sigma_s-z$  curves of Figure 3a.

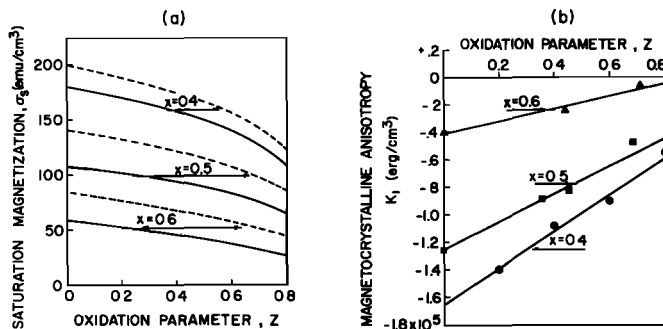


Fig. 3. Oxidation state dependences. (a) Saturation magnetization  $\sigma_s$  as a function of oxidation state  $z$ . The plots were derived from the  $\mu_B/\text{molecule}-z$  data of Readman and O'Reilly [1972] for  $x = 0.4$  and  $0.7$ . The dashed curves indicate data adjusted to  $290^\circ K$  by using the Weiss [1907]  $\sigma_s-T/T_c$  dependence, whereas the solid curves indicate data adjusted by using the  $\sigma_s-T/T_c$  plots of Stephenson [1972a]. (b) Magnetocrystalline anisotropy constant  $K_1$  versus oxidation parameter  $z$ . Data points were calculated from rotational hysteresis data of Readman and O'Reilly [1972] and Manson [1972] by using  $K_1 \propto H_p(z)\sigma_s(z)$ .

Rotational hysteresis data from *Readman and O'Reilly* [1972] allow an estimate of the dependence of magnetocrystalline anisotropy on oxidation state for titanomagnetite of  $x = 0.4$ . The maximum realizable shape anisotropy field for  $x = 0.4$  would be  $2\pi\sigma_s = 1.5$  koe for needle-shaped grains. The magnetocrystalline anisotropy field is of the order of  $(4/3)K_1/\sigma_s = 1.1$  koe. However, for the synthetic ball-milled samples,  $\Delta N_d$  should be substantially less than  $2\pi$ . Thus magnetocrystalline anisotropy should dominate for the synthetic  $x = 0.4$  samples. Since  $H_p$  (peak hysteresis loss field) is proportional to  $K_1/\sigma_s$ ,  $K_1$  can be calculated as a function of  $z$  by using  $K_1(z) \propto H_p(z)\sigma_s(z)$ . The resulting  $K_1$ - $z$  ( $x = 0.4$ ) curve is shown in Figure 3b. The rotational hysteresis data of *Manson* [1972] on  $x = 0.5$  and  $x = 0.6$  titanomagnetites allow calculation of  $H_p$ - $z$  plots from which  $K_1$ - $z$  can be obtained. The resulting  $K_1$ - $z$  curves are also shown in Figure 3b.

By means of the newly derived dependence of  $K_1$  and  $\sigma_s$  on oxidation state, room temperature relaxation times  $\tau_0(290^\circ\text{K}, z)$  can be determined by the use of (12) and (13). The results of these calculations are shown in Figures 4 and 5, which show the oxidation state at which  $\tau_0(290^\circ\text{K}, z)$  falls below  $10^4$  years as a function of the blocking temperature of the unoxidized grain ( $10^4$  years is small compared to the times of interest in studying the decay of marine magnetic anomalies). For example, an unoxidized titanomagnetite grain of composition  $x = 0.6$  whose coercive force is controlled by magnetocrystalline anisotropy and whose blocking temperature is initially  $350^\circ\text{K}$  will become superparamagnetic ( $\tau_0(290^\circ\text{K}, z) < 10^4$  years) when it is oxidized to titanomaghemite of  $z \hat{=} 0.5$ . The corresponding transition curves for shape-controlled anisotropy are shown in Figure 5(a, b).

Because the true  $\sigma_s$ - $T$  behavior will likely fall between the two dependences used in the relaxation calculations for grains with shape-controlled coercivity, the transition curves of Figure 5(a, b) represent limits within which the true shape anisotropy transition curves will fall. The necessary extrapolation of available  $K_1$ - $T$  data used in obtaining the transition curves of Figure 4 introduces some uncertainty into the calculations. An error in the estimated  $K_1$ - $T$  behavior would shift the transition curves

up or down the blocking temperature axis. However, since the blocking temperatures affected are within  $125^\circ\text{K}$  of the available experimental magnetocrystalline anisotropy data, no extensive extrapolation of  $K_1$ - $T$  is required, and the calculated transition curves of Figure 4 are thought to be accurate to within  $10^\circ$ - $20^\circ\text{K}$ .

## DISCUSSION

It appears that oxidation to titanomaghemite and the resulting transition of some grains from stable remanence carriers to superparamagnetic ones will be most important for  $x = 0.6$  titanomagnetites. For  $x = 0.4$  and  $x = 0.5$  the range of blocking temperatures affected is far below the Curie temperature. Conditions under which a significant portion of the NRM would be blocked at temperatures  $150^\circ$ - $250^\circ\text{K}$  below the Curie temperature are difficult to imagine. However, for  $x = 0.6$  (the composition of interest for oceanic basalts) the range of blocking temperatures affected is within  $100^\circ\text{K}$  of the Curie temperature. Blocking temperature distributions extending to  $100^\circ\text{K}$  below the Curie temperature are not at all uncommon.

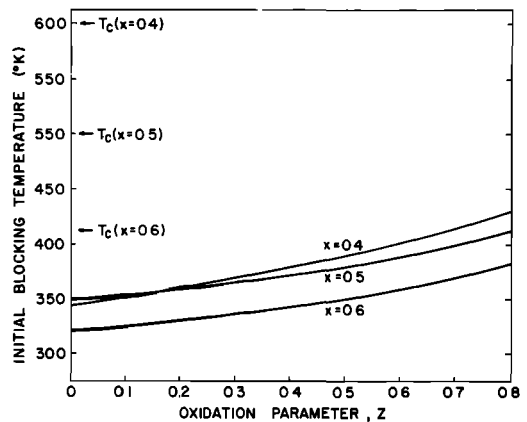


Fig. 4. Stable single-domain to superparamagnetic transition curves for  $x = 0.4, 0.5,$  and  $0.6$  titanomagnetites for grains in which coercivity is dominated by magnetocrystalline anisotropy. The lines show the degree of oxidation at which a titanomagnetite grain with initial blocking temperature given on the  $y$  axis will become superparamagnetic ( $\tau_0(290^\circ\text{K}, z) < 10^4$  years). For example, a titanomagnetite grain with  $x = 0.4$  and a blocking temperature of  $375^\circ\text{K}$  will be a stable single domain in the unoxidized state but will become superparamagnetic at room temperature if it is oxidized to titanomaghemite with  $z = 0.35$ .

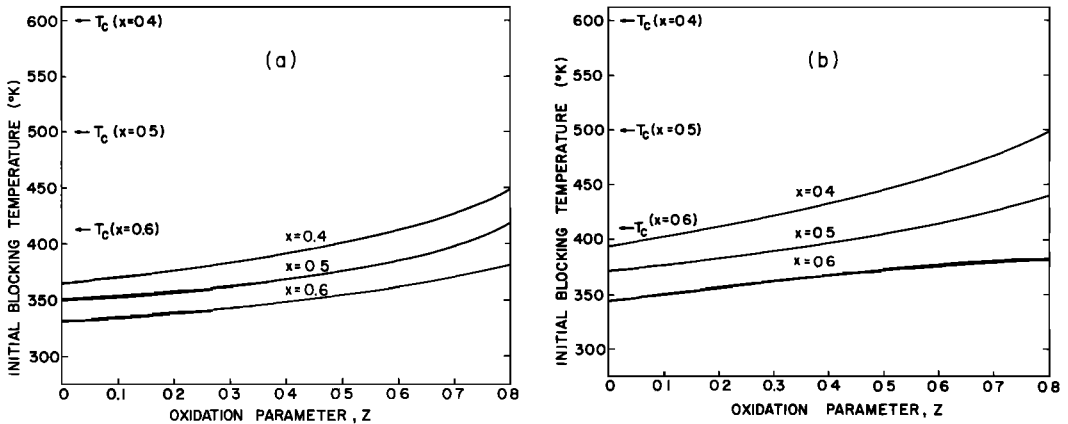


Fig. 5. Stable single-domain to superparamagnetic transition curves of  $x = 0.4, 0.5,$  and  $0.6$  titanomagnetites for grains with dominant shape anisotropy for the  $\sigma_s$ - $T$  behavior predicted by (a) *Stephenson [1972a]* and (b) *Weiss [1907]*. The curves illustrate the oxidation state at which a titanomagnetite grain of initial blocking temperature given on the  $y$  axis will become superparamagnetic ( $\tau_s(290^\circ\text{K}, z) < 10^4$  years). For example, in Figure 5a a titanomagnetite grain of  $x = 0.6$  and initial blocking temperature of  $350^\circ\text{K}$  will be stable single domain for  $z < 0.5$  but will become superparamagnetic if it is oxidized to a cation-deficient spinel of  $z \geq 0.5$ .

The range of blocking temperatures that will be affected obviously depends on the degree of oxidation. For titanomagnetite of  $x = 0.6$  and dominant magnetocrystalline anisotropy, grains with initial blocking temperatures of  $320^\circ\text{--}380^\circ\text{K}$  will become superparamagnetic (and therefore will not contribute to NRM intensity) when oxidation proceeds to  $z = 0.8$ . However, if titanomaghemitization proceeds only to  $z = 0.5$ , only grains with initial blocking temperatures of  $320^\circ\text{--}350^\circ\text{K}$  will become superparamagnetic. It should be noted that the bulk effect of oxidation will be to cancel the contribution of low blocking temperature grains to the NRM while only reducing the contribution of grains with higher  $T_B$  by the amount of the  $\sigma_s$  decrease. This effect could help to explain the increase in mean blocking temperature with distance from the median valley noted by *Irving [1970]*.

It is interesting to note that the evolution of thermomagnetic curves with degree of oxidation shown in Figure 5 of *Readman and O'Reilly [1972]* along with the attendant Curie point increase can nicely explain the increased blocking temperature of grains whose initial  $T_B$  is close to the Curie temperature. For example, an  $x = 0.6$  grain with shape-controlled coercivity and blocking temperature within  $10^\circ\text{--}20^\circ\text{C}$  of the Curie point will be very strongly

blocked at room temperature and will not become superparamagnetic during low-temperature oxidation. Although the room temperature saturation magnetization  $\sigma_s$  of this grain will decrease during oxidation, the increasing Curie point will change the  $\sigma_s$ - $T$  curve so as to produce an increase in blocking temperature. Similar changes in  $K_1$ - $T$  with increased Curie point will also produce an increase in  $T_B$  for grains with magnetocrystalline-dominated coercivity and initial blocking temperature close to the Curie temperature. Thus the oxidation-induced stable single-domain to superparamagnetic transition of grains with low blocking temperatures along with the increasing blocking temperature of the remaining stable single-domain grains will yield the increase in mean blocking temperature with distance from the median valley that was observed by *Irving [1970]*.

Unfortunately, the quantitative importance of the calculations above in accounting for the large NRM intensity decrease of dredged basalts with age is difficult to ascertain. First, the degree of oxidation of the dredge samples is not accurately known because the determinations of cell edge, Curie temperature, and saturation magnetization required to place these samples within the cation-deficient field are very difficult to perform on natural samples.



Second, the blocking temperature distribution of the natural samples is not accurately known. However, for the decrease in saturation magnetization alone to account for the 90% decrease in natural remanent intensity observed by *Irving et al.* [1970], low-temperature oxidation to greater than  $z = 0.8$  would be required. An additional NRM decrease resulting from the stable single-domain to superparamagnetic transition of low blocking temperature grains would allow the observed NRM decrease to be accounted for by a much lower (and more reasonable) degree of oxidation.

Inspection of Figures 4 and 5 indicates that, if the blocking temperature distribution in the fresh basalts of interest ( $x \approx 0.6$ ) extends to only 60°K below the Curie temperature, little oxidation is required before a significant portion of the previously stable remanence carriers will become superparamagnetic. For  $x = 0.6$  grains with dominant magnetocrystalline anisotropy, oxidation to  $0.5 \leq z \leq 0.8$  will cause grains in the initial blocking temperature range 350°–380°K to become superparamagnetic. For  $x = 0.6$  grains with dominant shape anisotropy, oxidation into the range  $0.2 \leq z \leq 0.8$  would progressively initiate the stable single-domain to superparamagnetic transition for the blocking temperature range 340°–380°K. Thus, given a distribution of blocking temperatures appreciably below the Curie point, oxidation to titanomaghemite will cause a significant portion of the originally stable carriers of NRM to become superparamagnetic.

The rapid quenching of oceanic pillow basalts produces small titanomagnetite grains that are efficient TRM carriers (in the fresh material) and are susceptible to low-temperature oxidation. Rapid quenching will also assure a wide grain size distribution. This grain size distribution will result in a spread of blocking temperatures appreciably below the Curie temperature. Therefore the quenching process assures that a significant portion of the NRM carriers in fresh pillow lavas will fall prey to the transition to superparamagnetism outlined above as low-temperature oxidation proceeds.

As was mentioned previously, the increase in the mean blocking temperature with distance from the median valley reported by *Irving et al.* [1970] and *Irving* [1970] could result from the oxidation-induced stable single-domain to super-

paramagnetic transition of the low blocking temperature grains along with the increased blocking temperature of the remaining stable grains. However, the parallel increase in resistance to a.f. demagnetization reported by *Irving et al.* [1970] for the dredged basalts and similar increase in a.f. demagnetization resistance of the weathered region in the single pillow basalt studied by *Marshall and Cox* [1972] is more difficult to explain. If coercive force is due to shape anisotropy, a.f. demagnetization resistance should decrease as  $\sigma_s$  decreases with oxidation. However, if coercivity is dominated by magnetocrystalline anisotropy and  $K_1$  decreases more slowly than  $\sigma_s$ ,  $K_1/\sigma_s$  would increase with oxidation, and a.f. demagnetization resistance would increase. Although peak rotational hysteresis loss field  $H_p$  decreases with oxidation for  $x \leq 0.55$ ,  $H_p$  increases during oxidation for  $x \geq 0.6$  [*Manson*, 1972]. This increase in  $H_p$  indicates a corresponding increase in microscopic coercivity with oxidation for  $x \geq 0.6$ . *Marshall and Cox* [1972] have suggested that inhomogeneous oxidation could produce internal strains that would produce higher coercivity through magnetostrictive effects.

The effects of internal stress on the coercivity of stoichiometric titanomagnetites in the composition range  $x = 0.5$ – $0.6$  may be significant. Because the magnetostrictive constant  $\lambda_{100}$  is increasing in the range  $0.4 \leq x \leq 0.6$  [*Syono*, 1965], whereas  $\sigma_s$  is decreasing, and magnetostrictive  $H_e = 3\lambda\sigma/\sigma_s$ , where  $\sigma$  is stress, internal stress may become an important contributor to coercivity in the  $x = 0.6$  composition region. The dependence of  $\lambda$  on temperature (above room temperature) and oxidation state is unknown. Both magnetocrystalline anisotropy and magnetostriction arise from the energy dependence of the electron probability distributions on the direction of the orbital angular momentum vector  $\mathbf{L}$  and the interatomic spacing. These energy dependences are manifested in macroscopic direction and stress dependences of the magnetic moment via spin-orbit coupling. Given the similarity in origin of magnetostrictive and magnetocrystalline anisotropy, it would be not only reasonable but even imperative to predict a similarity in the dependences of  $\lambda$  and  $K_1$  on oxidation state. Thus the possibility that the initial coercivity of  $x = 0.6$  titanomagnetites could be due to magnetostriction will not affect

the qualitative aspects of the theory outlined above. A decrease in  $\lambda$  with oxidation would produce the same stable single-domain to superparamagnetic transition in the lower blocking temperature grains as is predicted by the decrease of  $K_1$  with  $z$ .

#### CONCLUSION

Although several extrapolations and interpolations of available data are required in the calculations of activation volumes and room temperature relaxation times, it seems clear that the outlined theory of stable single-domain to superparamagnetic transition during low-temperature oxidation can help explain the large NRM intensity decrease with increasing age observed in dredged oceanic basalts. The resulting diminished contribution of low blocking temperature grains along with increased  $T_B$  of the remaining stable single-domain grains could also help to explain the increased mean blocking temperature with increasing distance from the median valley. The decreasing contribution to marine magnetic anomalies of the upper layer in the two-layer model of oceanic crust proposed by Cox *et al.* [1972] could also be aided by the mechanism above of NRM intensity decrease.

Thus the decrease in natural remanence intensity observed in oceanic basalts may be due not only to the decrease in saturation magnetization by oxidation of the stable single-domain grains as proposed by Marshall and Cox [1972]. Oxidation to a cation-deficient spinel will also decrease the number of stable NRM carriers by causing a significant portion of the titanomagnetite grains to become superparamagnetic as they are oxidized.

*Acknowledgments.* I am indebted to Subir Banerjee for many helpful discussions of this project and for critically reviewing the manuscript. I also thank Peter Shive for reading the manuscript in preliminary form.

This work was supported by NSF grant GA 35249.

#### REFERENCES

Banerjee, S. K., Decay of marine magnetic anomalies by ferrous ion diffusion, *Nature Phys. Sci.*, **229**, 181, 1971.  
 Banerjee, S. K., Rock magnetic aspects of marine magnetic anomalies, *Comments Earth Sci. Geophys.*, **2**, 169, 1972.  
 Carmichael, C. M., The mid-Atlantic ridge near 45°N, **7**, Magnetic properties and opaque min-

eralogy of dredged samples, *Can. J. Earth Sci.*, **7**, 239, 1970.  
 Chikazumi, S., *Physics of Magnetism*, pp. 136-138, John Wiley, New York, 1964.  
 Cox, A., R. J. Blakely, and J. D. Phillips, A two-layer model for marine magnetic anomalies (abstract), *Eos Trans. AGU*, **53**, 974, 1972.  
 Evans, M. E., and M. L. Wayman, The mid-Atlantic ridge near 45°N, **19**, An electron microscope investigation of the magnetic minerals in basalt samples, *Can. J. Earth Sci.*, **9**, 671, 1972.  
 Irving, E., The mid-Atlantic ridge near 45°N, **14**, Oxidation and magnetic properties of basalt; Review and discussion, *Can. J. Earth Sci.*, **7**, 1528, 1970.  
 Irving, E., W. A. Robertson, and F. Aumento, The mid-Atlantic ridge near 45°N, **6**, Remanent intensity, susceptibility, and iron content of dredged samples, *Can. J. Earth Sci.*, **7**, 226, 1970.  
 Manson, A., Rotational hysteresis measurements on oxidized synthetic and natural titanomagnetites, Ph.D. thesis, Univ. of Newcastle upon Tyne, Newcastle, England, 1972.  
 Marshall, M., and A. Cox, Magnetic changes in pillow basalt due to sea floor weathering, *J. Geophys. Res.*, **77**, 6459, 1972.  
 Neel, L., Some theoretical aspects of rock magnetism, *Advan. Phys.*, **4**, 191, 1955.  
 O'Reilly, W., and S. K. Banerjee, Cation distribution in titanomagnetites  $(1-x)\text{Fe}_3\text{O}_4-x\text{Fe}_2\text{TiO}_4$ , *Phys. Lett.*, **17**, 237, 1965.  
 Park, J. K., and E. Irving, The mid-Atlantic ridge near 45°N, **12**, Coercivity, secondary magnetization, polarity, and thermal stability of dredged samples, *Can. J. Earth Sci.*, **7**, 1499, 1970.  
 Readman, P. W., and W. O'Reilly, Magnetic properties of oxidized (cation deficient) titanomagnetites (Fe, Ti,  $\square$ ) $_2\text{O}_4$ , *J. Geomagn. Geoelec.*, **24**, 69, 1972.  
 Schaeffer, R. M., and E. J. Schwarz, The mid-Atlantic ridge near 45°N, **9**, Thermomagnetism of dredged samples of igneous rocks, *Can. J. Earth Sci.*, **7**, 268, 1970.  
 Stephenson, A., Spontaneous magnetization curves and Curie points of cation deficient titanomagnetites, *Geophys. J.*, **29**, 91, 1972a.  
 Stephenson, A., Spontaneous magnetization curves and Curie points of spinels containing two types of magnetic ion, *Phil. Mag.*, **25**, 1213, 1972b.  
 Syono, Y., Magnetocrystalline anisotropy and magnetostriction of  $\text{Fe}_3\text{O}_4$ - $\text{Fe}_2\text{TiO}_4$  series—With special application to rock magnetism, *Jap. J. Geophys.*, **4**, 71, 1965.  
 Weiss, P., Hypothesis of the molecular field and ferromagnetic properties, *J. Phys. Radium*, **6**, 661, 1907.

(Received February 9, 1973;  
 revised June 28, 1973.)